arXiv:1210.1661v1 [cond-mat.supr-con] 5 Oct 2012

On intraband superconducting instability smeared by interband interaction

Artjom Vargunin, Küllike Rägo, and Teet Örd*
Institute of Physics, University of Tartu, 4 Tähe Street, 51010 Tartu, Estonia

(Dated: October 8, 2012)

We study several manifestations of former intrinsic phase transition in the band with weaker superconductivity by analysing thermodynamics of a two-gap system. We show that weak interband interaction acts as external field on that critical point. At that, the corresponding singularities of the thermodynamic functions become smeared and all located at different temperatures.

PACS numbers: 74.25.Bt, 05.70.Jk, 74.20.-z
Keywords: Criticality; Interband interaction; Two-band superconductor; Thermodynamics.

I. INTRODUCTION

After an extension of the Bardeen-Cooper-Schrieffer theory to the case of overlapping bands[1] multi-component superconductivity was confirmed for many groups of materials: metals[2], doped $SrTiO_3$[3], cuprates[4], MgB_2[5–7] and pnictides[8] among others.

In several two-band systems both gaps behave with temperature in a very similar manner throughout the whole superconducting phase[5,9]. At the same time, a two-band model has distinct intraband critical points. Therefore, there exists a temperature region where stronger band (i.e. band with stronger superconductivity) is intrinsically superconducting (active), but weaker one is not yet (passive). Arbitrarily weak interband coupling fixes single phase transition for joint superconducting condensate by penetration of the Cooper pairs from an active band into the passive one inducing there superconductivity (interband proximity effect). As a result, for tiny interband pairing the gap in the weaker band inflects somewhere below critical point of the joint condensate and then slowly reduces until the phase transition temperature is reached.

There exists a number of experimental verifications for the behavior of that type. Almost vanishing interband interaction was observed in Nb doped $SrTiO_3$[3,10] and in $NbSe_2$[11]. The conductivity and superfluid density data points to the nearly decoupled bands in V_3Si[12,13] and $FeSe_{1-x}$[14]. The studies of nickel borocarbides[15] and sesquicarbides[16] are in good agreement with prediction of weakly interacting two-band scenario. The dependence of resistive superconducting transition on the current direction in UNi_2Al_3 is explained in terms of weakly coupled order parameters[17]. It has been revealed that the gap in the inner planes of multilayered system Cu1234 fully opens below 117 K, but that in the outer planes only below 60 K[18]. An impact of the coupling between order parameters on the superconductivity in layered mesoscopic rings was illustrated by proximitization between two participating layers[19]. The change of interband interaction with doping was demonstrated in $Mg_{1-x}Al_xB_2$ leading to the appearance of a "tail" at the π-gap[20]. Similar feature was found also in iron-based oxypnictide $LaFeAsO_{1-x}F_x$[21].

In spite of single superconducting instability of a two-band system the memory about intrinsic criticality of the weaker band can be still visible in the heat capacity curve[22,23], coherence lengths[24], and relaxation times[25] of order parameters fluctuations as additional maximum below phase transition temperature. An impact of tiny interaband pairing on the separation between vortices[26], vortex size[27], and type-1.5 superconductivity[28] is also noteworthy.

The evolution of the gap healing length, analysed recently for two-band scenario[29], reveals that interband coupling plays the role of the source field governing intrinsic criticality of the weaker band similarly to an external magnetic field for ferromagnetic materials or an external electric field for ferroelectric systems. More direct characteristics of superconductivity should be examined to confirm that important conclusion.

In the present contribution we perform a detailed analysis of the smearing of intraband superconducting instability seen in the temperature behaviour of thermodynamic functions. In this respect the relevant two-band materials are discussed.

II. THERMODYNAMICS OF A TWO-GAP SYSTEM

We start with the Hamiltonian of a homogeneous two-band superconductor with intra- and interband pair transfer interactions,

$$H = \sum_{\alpha\mathbf{k}s} \tilde{\epsilon}_\alpha(\mathbf{k}) a^+_{\alpha\mathbf{k}s} a_{\alpha\mathbf{k}s} - \frac{1}{V} \sum_{\alpha\alpha'} \sum_{\mathbf{k}\mathbf{k}'} W_{\alpha\alpha'} a^+_{\alpha\mathbf{k}\uparrow} a^+_{\alpha-\mathbf{k}\downarrow} a_{\alpha'-\mathbf{k}'\downarrow} a_{\alpha'\mathbf{k}'\uparrow}, \qquad (1)$$

where $\tilde{\epsilon}_\alpha = \epsilon_\alpha - \mu$ is the electron energy in the band $\alpha = 1, 2$ relative to the chemical potential μ; V is the volume of superconductor and $W_{\alpha\alpha'}$ are the matrix elements of intraband attraction ($W_{\alpha\alpha} > 0$) or interband ($\alpha \neq \alpha'$) interaction. It is supposed that the chemical potential is located in the region of the bands overlapping. We assume that (effective) electron-electron interactions are nonzero only in the layer $\mu \pm \hbar\omega_D$ and that the interaction constants are independent on electron wave vector in this layer. We also take $W_{12} = W_{21}$.

To calculate the partition function $Z = \mathrm{Sp}\exp\left(\frac{-H}{k_\mathrm{B}T}\right)$ we use the Hubbard-Stratonovich transformation[30] by means of which one linearizes and diagonalizes an exponent in Z by introducing complex integration variables. For sufficiently small interband interaction $W^2 = W_{11}W_{22} - W_{12}^2 > 0$ the static path approximation reads as

$$Z = \left(\frac{V}{\pi k_B T W}\right)^2 \int\limits_{-\infty}^{\infty} \exp\left(-\frac{V\tilde{f}}{k_\mathrm{B}T}\right) \mathrm{d}\delta_1'\mathrm{d}\delta_1''\mathrm{d}\delta_2'\mathrm{d}\delta_2'', \quad (2)$$

$$\tilde{f} = \sum_\alpha \left[\frac{1}{V}\sum_\mathbf{k}\left(\tilde{\epsilon}_\alpha(\mathbf{k}) - 2k_B T \ln\left(2\mathrm{ch}\frac{\tilde{E}_\alpha(\mathbf{k})}{2k_B T}\right)\right)\right.$$
$$\left. + \frac{W_{3-\alpha,3-\alpha}}{W^2}|\delta_\alpha|^2 - \frac{W_{\alpha,3-\alpha}}{W^2}(\delta_\alpha'\delta_{3-\alpha}' + \delta_\alpha''\delta_{3-\alpha}'')\right]. \quad (3)$$

Here the integration variables δ_α' and δ_α'' are treated as real and imaginary parts of the non-equilibrium complex order parameters δ_α, and

$$\tilde{E}_\alpha(\mathbf{k}) = \sqrt{\left(\tilde{\epsilon}_\alpha(\mathbf{k}) - \frac{W_{\alpha\alpha}}{2V}\right)^2 + |\delta_\alpha|^2}. \quad (4)$$

Next we find the equilibrium free energy density $f = -k_\mathrm{B}T\frac{\ln Z}{V}$ for a macroscopic superconductor ($V \to \infty$). First, we perform an integration in Z over the phases of non-equilibrium order parameters and then go to infinite volume. In this process one obtains the integration over wave vector $\mathbf{k}$ instead of summation in $\tilde{f}$, which we replace with the integration over energy. Free energy density f becomes

$$f = f_\mathrm{n} + \sum_\alpha \left[-4k_\mathrm{B}T\rho_\alpha \int\limits_0^{\hbar\omega_\mathrm{D}} \ln\frac{\mathrm{ch}\frac{E_\alpha(\tilde{\epsilon}_\alpha)}{2k_\mathrm{B}T}}{\mathrm{ch}\frac{\tilde{\epsilon}_\alpha}{2k_\mathrm{B}T}}\mathrm{d}\tilde{\epsilon}_\alpha \right.$$
$$\left. + \frac{W_{3-\alpha,3-\alpha}}{W^2}\Delta_\alpha^2 - \frac{|W_{\alpha,3-\alpha}|}{W^2}\Delta_\alpha\Delta_{3-\alpha}\right]. \quad (5)$$

Here $E_\alpha(x) = \sqrt{x^2 + \Delta_\alpha^2}$, where Δ_α is the modulus of equilibrium order parameter, i.e. the value of $|\delta_\alpha|$ which minimizes non-equilibrium free energy density $\tilde{f}$. The quantity f_n corresponds to the free energy density in the absence of superconductivity, and ρ_α is the density of electron states taken to be constant in the narrow integration layer around the Fermi level.

The minimization of non-equilibrium free energy leads to the equations for equilibrium order parameters

$$\frac{W_{3-\alpha,3-\alpha}}{W^2}\Delta_\alpha - \rho_\alpha\Delta_\alpha \int\limits_0^{\hbar\omega_\mathrm{D}} \mathrm{th}\frac{E_\alpha(\tilde{\epsilon})}{2k_\mathrm{B}T}\frac{\mathrm{d}\tilde{\epsilon}}{E_\alpha(\tilde{\epsilon})} = \frac{|W_{\alpha,3-\alpha}|}{W^2}\Delta_{3-\alpha}. \quad (6)$$

If interband interaction is absent, the latter system splits into two independent equations which describe intrinsic superconductivity in the bands. The corresponding critical temperatures equal $T_{\mathrm{c}\alpha} = 1.13\frac{\hbar\omega_\mathrm{D}}{k_\mathrm{B}}e^{-\frac{1}{\rho_\alpha W_{\alpha\alpha}}}$. However, if interband coupling is present the critical temperatures $T_{\mathrm{c}\alpha}$ transform into

$$T_{\mathrm{c}\mp} = 1.13\frac{\hbar\omega_\mathrm{D}}{k_\mathrm{B}}e^{-\frac{2}{\rho_1 W_{11} + \rho_2 W_{22} \pm \sqrt{(\rho_1 W_{11} - \rho_2 W_{22})^2 + 4\rho_1\rho_2 W_{12}^2}}}, \quad (7)$$

where $T_{\mathrm{c}-} > T_{\mathrm{c}+}$. With $|W_{12}|$ increase the temperature $T_{\mathrm{c}-}$ increases and $T_{\mathrm{c}+}$ decreases approaching zero as $W \to 0$. For $W_{12} \to 0$ one has $T_{\mathrm{c}-} \to T_{\mathrm{c}1}$ and $T_{\mathrm{c}+} \to T_{\mathrm{c}2}$, if $T_{\mathrm{c}1} > T_{\mathrm{c}2}$. Note that for a superconductor with interacting bands there is only one phase transition temperature $T_\mathrm{c} = T_{\mathrm{c}-}$. However, the point $T_{\mathrm{c}+}$ is also meaningful, because below $T_{\mathrm{c}+}$ the metastable superconducting states or saddle-points of non-equilibrium free energy appear[31]. These peculiarities can be reflected in the behaviour of superconducting fluctuations.

Thermodynamics of the system related to superconductivity is entirely described by excess free energy density $\Delta f = f - f_\mathrm{n}$ and its temperature derivatives, e.g. excess specific entropy $\Delta s = -\Delta f'$ and specific heat capacity $\Delta c = -T\Delta f''$. For the degenerate electron gas one has $s_\mathrm{n} = c_\mathrm{n} = \gamma_\mathrm{S}T$, where $\gamma_\mathrm{S} = \frac{2}{3}\pi^2 k_\mathrm{B}^2(\rho_1 + \rho_2)$ is the Sommerfeld constant. Therefore, the extrema and inflection points of Δs coincide in the temperature scale with zeros and extrema of $\frac{\Delta c}{c_\mathrm{n}}$, correspondingly. It is also worth to mention that the quantities Δf, Δs and Δc may be represented by means of additive contributions from the relevant bands.

III. RESULTS AND DISCUSSIONS

A. Numeric study

Below we examine thermodynamic properties of a two-gap superconductor with extremely weak interband coupling. In such a system the joint superconducting state is close to the splitting into two independent condensates. For illustration we consider the following set of intraband parameters: $\rho_{1,2} = (1, 0.9)(\mathrm{eV}\cdot\mathrm{cell})^{-1}$, $W_{11,22} = 0.3\ \mathrm{eV}\cdot\mathrm{cell}$ and $\mathrm{cell} = 0.1\ \mathrm{nm}^3$. In this case $T_{\mathrm{c}2} = 0.69T_{\mathrm{c}1}$.

Fig. 1 shows the changes of the gaps, excess entropy and heat capacity with intra- and interband interactions calculated numerically on the basis of Eqs. (5)-(6). By turning interband coupling on, the intrinsic criticality in the weaker band becomes smeared by interband proximity effect and both gaps go to zero at very same point $T_\mathrm{c} = T_{\mathrm{c}-}$, i.e. the vanishing of the smaller gap Δ_2 at $T_{\mathrm{c}2}$ changes into inflection near $T_{\mathrm{c}+} \approx T_{\mathrm{c}2}$. That inflection indicates the crossover from active to passive regime of the weaker band and it disappears as interband interaction exceeds some value.

To interpret the temperature behaviour of entropy and heat capacity it is convenient to visualize band contributions, see panels 2b,c, and 3b,c in Fig. 1. For tiny interband coupling these contributions start to develop considerably below different temperatures $T_{\mathrm{c}-,+} \approx T_{\mathrm{c}1,2}$

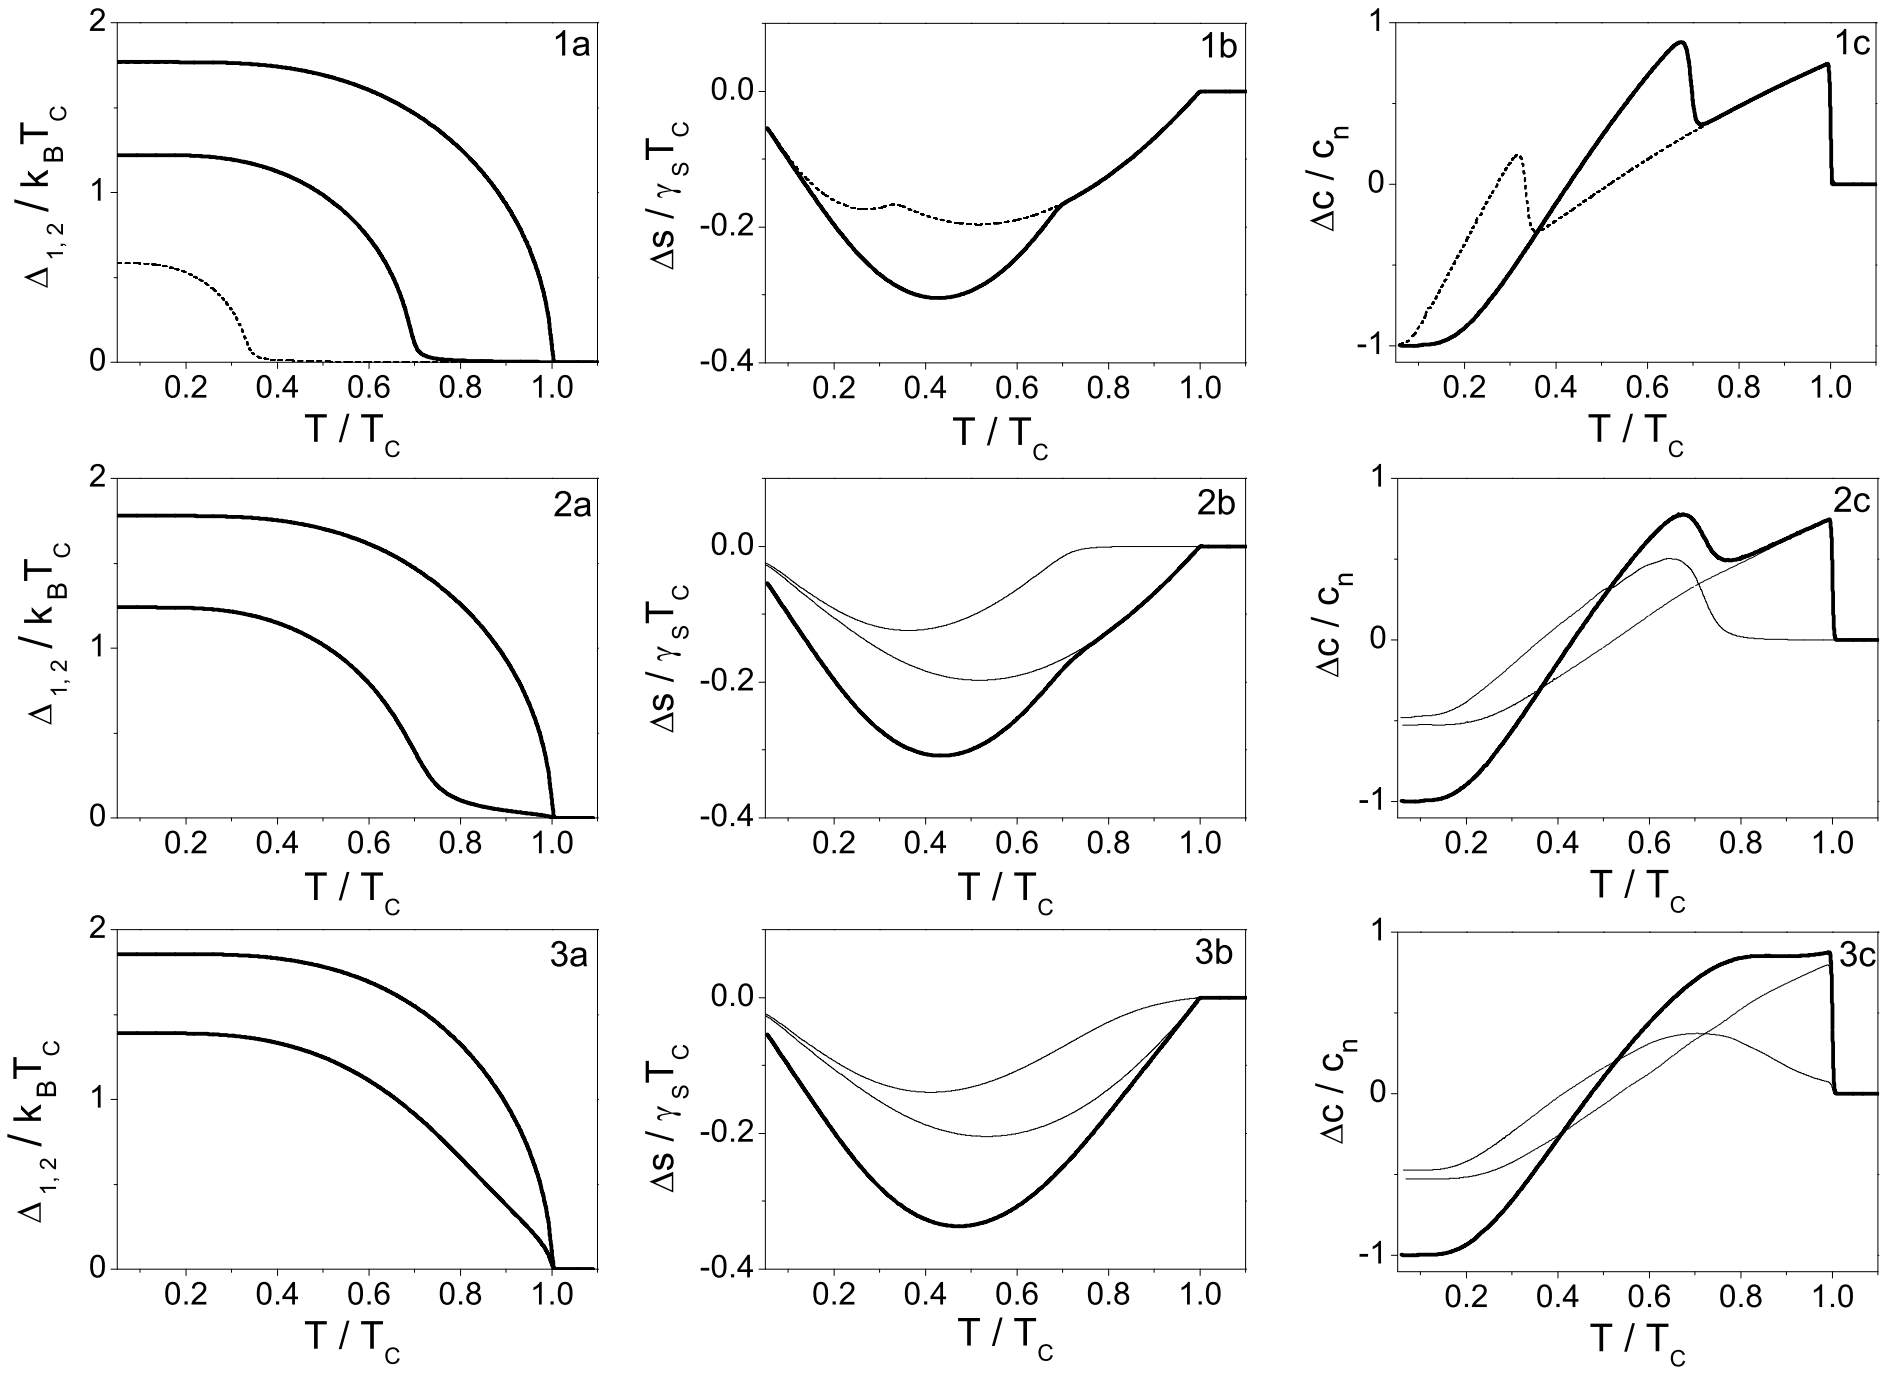

FIG. 1. The plots of the gaps (a), excess specific entropy (b) and normalized excess specific heat capacity (c) vs reduced temperature for $W_{12} = 0.0001$ eV $\cdot$ cell (1), $W_{12} = 0.001$ eV $\cdot$ cell (2) and $W_{12} = 0.01$ eV $\cdot$ cell (3). In the first row of figures the dashed lines denote the corresponding quantities for slightly weaker coupling in the second band $W_{22} = 0.25$ eV $\cdot$ cell ($T_{\mathrm{c}2} = 0.33 T_{\mathrm{c}1}$). In Fig. (1a) the larger gaps flow together for the constants W_{22} considered. In the second and third rows of figures the thin lines denote band contributions to the excess entropy and specific heat capacity.

resulting in the substantial increment for entropy and the non-monotonicity for heat capacity in the vicinity of $T_{\mathrm{c}+}$. These features demonstrate again the criticality of the weaker band smeared by interband interaction. The latter was observed also experimentally[32]. For sufficiently strong interband pairings both bands have comparable contributions to the joint superconductivity up to T_{c}. Note that the presence of several components of superconductivity makes the standard Bardeen-Cooper-Schrieffer theory inappropriate for the systems considered[7,33]. Well-known universal ratios become also violated[23,34].

Interestingly, the certain configuration of intraband interaction channels together with sufficiently weak interband coupling result in the local maximum of entropy in superconducting state, see the first row of panels in Fig. 1. In this case $\frac{\Delta c}{c_{\mathrm{n}}} \sim \frac{\mathrm{d}\Delta s}{\mathrm{d}T}$ crosses zero below T_{c} three times. Similar effect was revealed in Cu1234[35].

Whereas both sharp non-monotonic behaviour of heat capacity and the kink of the smaller gap are the footprints of intrinsic phase transition in the weaker band, should one identify the maximum of $\frac{\Delta c}{c_{\mathrm{n}}}$ below T_{c} with $T_{\mathrm{inf}}^{\Delta_2}$, the temperature where Δ_2 inflects? Numeric calculations demonstrate (see Fig. 2a) that these points match only approximately and not for extremely weak interband interactions. The minimum of $\frac{\Delta c}{c_{\mathrm{n}}}$ below T_{c} is more farther off $T_{\mathrm{inf}}^{\Delta_2}$. We see that neither the inflections for $\Delta f'(T)$ nor for $\Delta f''(T)$ reproduce the position of the kink of $\Delta_2(T)$, however, it is the function $\Delta f^{\mathrm{III}}(T)$ which inflects at $T_{\mathrm{inf}}^{\Delta_2}$ for extremely weak interband pairings. In the vicinity of $T_{\mathrm{c}+}$ the contribution from stronger band to $\Delta f^{\mathrm{III}}(T)$ is practically temperature independent and remarkably smaller than that from weaker band. The latter function has a maximum at the temperatures considered which flattens as interband interaction increases.

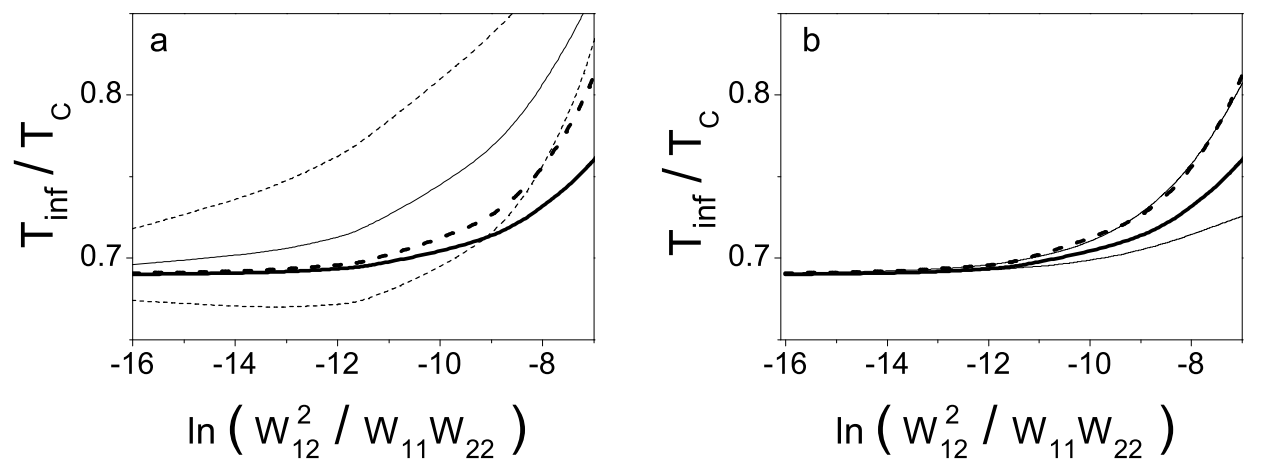

FIG. 2. (a) Nearest to $T_{\mathrm{c}+}$ inflection points for $\Delta f'$ (two thin dashed curves for maximum and minimum of $\frac{\Delta c}{c_{\mathrm{n}}}$), $\Delta f''$ (thin solid curve), Δf^{III} (thick solid curve) and for Δ_2 (thick dashed curve) vs interband constant. (b) Inflection points for Δ_2 (thick dashed curve) and for Δf^{III} (thick solid curve) compared to the approximations given by the analytic formulas (11) and (13) (thin solid curves).

Material	$\sqrt{\frac{W_{12}^2}{W_{11}W_{22}}}$	$\frac{T_{\mathrm{c}+}}{T_{\mathrm{c}}}$	$\frac{T_{\max}^{\frac{\Delta c}{c_{\mathrm{n}}}}-T_{\mathrm{inf}}^{\Delta_2}}{T_{\mathrm{c}}}$	$\frac{T_{\min}^{\frac{\Delta c}{c_{\mathrm{n}}}}-T_{\mathrm{inf}}^{\Delta_2}}{T_{\mathrm{c}}}$	$\frac{T_{\mathrm{inf}}^{\Delta f''}-T_{\mathrm{inf}}^{\Delta_2}}{T_{\mathrm{c}}}$	$\frac{T_{\mathrm{inf}}^{\Delta f^{\mathrm{III}}}-T_{\mathrm{inf}}^{\Delta_2}}{T_{\mathrm{c}}}$
LiFeAs	0.096[36]	0.310				-0.175
V_3Si	0.014[12]	0.490	0.009	0.102	0.050	-0.021
$FeSe_{1-x}$	0.002[14]	0.376	-0.019	0.062	0.017	-0.004

TABLE I. The relative position of the nearest to $T_{\mathrm{c}+}$ inflection points for $\Delta f'$ (both maximum and minimum of $\frac{\Delta c}{c_{\mathrm{n}}}$ are considered), $\Delta f''$ and for Δf^{III} in case of LiFeAs, V_3Si and $FeSe_{1-x}$. Material parameters used in numeric calculation were taken from the references shown.

Next we compare the positions of the relevant peculiarities for two-band superconducting materials under interest, see Table I. In LiFeAs heat capacity behaves monotonically below T_{c} and $T_{\mathrm{inf}}^{\Delta_2}$ can be found only approximately, i.e. in this system W_{12} is sufficiently large. V_3Si can be considered as a compound with moderately weak interband coupling due to the closeness of $T_{\mathrm{inf}}^{\Delta_2}$ and the position of maximum of $\frac{\Delta c}{c_{\mathrm{n}}}$. This type of behaviour is described by r.h.s. of Fig. 2a. $FeSe_{1-x}$ is a system where the kink of the smaller gap appears close to the inflection point of Δf^{III} (middle part of Fig. 2a). Our estimations indicate also that entropy of $FeSe_{1-x}$ should have a local maximum in superconducting phase approximately at $0.41T_{\mathrm{c}} = 3.4$ K. This feature was discussed above in connection with dashed lines in the first row of panels in Fig. 1.

B. Analytic treatment

Below we confirm numeric result about the discrepancy between the positions of the kink of the smaller gap and heat capacity maximum in the case which can be treated analytically. By starting with non-equilibrium free energy $\tilde{f}$ expanded in powers of δ_α, we obtain for macroscopic superconductor

$$\Delta f = \sum_\alpha \Big(a_\alpha \Delta_\alpha^2 + \frac{b_\alpha}{2}\Delta_\alpha^4 - \gamma \Delta_\alpha \Delta_{3-\alpha} \Big), \tag{8}$$

where

$$a_\alpha = \frac{W_{3-\alpha,3-\alpha}}{W^2} - \rho_\alpha \ln \frac{1.13\hbar\omega_{\mathrm{D}}}{k_{\mathrm{B}}T}, \tag{9}$$

and $b_\alpha = \frac{0.11\rho_\alpha}{(k_{\mathrm{B}}T)^2}$, $\gamma = \frac{|W_{12}|}{W^2}$. This approximation works perfectly in the vicinity of critical point. However, as we do not expand the parameters a_α and b_α in powers of $T_{\mathrm{c}} - T$, we have at least qualitatively correct picture also further off the critical temperature[37]. In particular, one ascertains numerically that corresponding gap equations

$$a_\alpha \Delta_\alpha + b_\alpha \Delta_\alpha^3 = \gamma \Delta_{3-\alpha} \tag{10}$$

still describe an inflection in the behaviour of $\Delta_2(T)$, while the derivatives of expressions (8) and (5) are quite close for relevant temperatures. Note that alternative approaches based on the expansion in powers of $T_{\mathrm{c}} - T$ cannot reproduce the kink of the smaller gap[38].

Next we solve analytically the system (10) in the vicinity of $T_{\mathrm{c}+}$ for extremely small interband couplings, see Appendix. The solution found for $\Delta_2(T)$ is characterized by the following inflection point

$$T_{\mathrm{inf}}^{\Delta_2} = T_{\mathrm{c}+}\left(1 + \frac{9y_+^{\{\frac{1}{3}\}2}}{2A_+^{\{0\}2}} + \frac{3B_+^{\{1\}}}{2A_+^{\{0\}}y_+^{\{\frac{1}{3}\}}}\right), \tag{11}$$

where

$$\begin{aligned} y_+^{\{\frac{1}{3}\}} &= A_+^{\{0\}} t^{\frac{1}{3}} w^{\frac{1}{3}}, \qquad A_+^{\{0\}} = 9.4\big(k_{\mathrm{B}}T_{\mathrm{c}2}\big)^2, \\ B_+^{\{1\}} &= A_+^{\{0\}2} w, \end{aligned} \tag{12}$$

and $t = \ln \frac{T_{\mathrm{c}1}}{T_{\mathrm{c}2}}$, $w = \Big(\frac{W_{12}}{\rho_2 W_{11} W_{22}}\Big)^2$. The temperature $T_{\mathrm{inf}}^{\Delta_2}$ contains the lowest order correction to $T_{\mathrm{c}+}$ proportional to $W_{12}^{\frac{4}{3}}$. It proves that the smaller gap as a function of temperature inflects in the vicinity of $T_{\mathrm{c}+}$ if interband interaction is extremely weak.

By using solutions $\Delta_\alpha(T)$ we analyse the temperature dependence of free energy (8). For the inflection point of $\Delta f^{\mathrm{III}}(T)$ we get

$$T_{\mathrm{inf}}^{\Delta f^{\mathrm{III}}} = T_{\mathrm{c}+}\left(1 + \frac{3B_+^{\{1\}}}{2A_+^{\{0\}}y_+^{\{\frac{1}{3}\}}}\right). \tag{13}$$

Analytic expressions (11) and (13) approximate values found numerically strikingly well, see Fig. 2b. Our calculation confirms also that functions $\Delta f^{\mathrm{III}}(T)$ and $\Delta f^{\mathrm{IV}}(T)$ vanish remarkably farther off $T_{\mathrm{c}+}$ as opposed to $\Delta f^{\mathrm{V}}(T)$. In other words, the inflection points of entropy Δs or heat capacity $\frac{\Delta c}{c_{\mathrm{n}}}$ do not appear sufficiently close to $T_{\mathrm{c}+}$ for tiny interband interactions.

The temperatures $T_{\mathrm{inf}}^{\Delta_2}$ and $T_{\mathrm{inf}}^{\Delta f^{\mathrm{III}}}$ given in Eqs. (11)-(13) coincide, if

$$\frac{3y_+^{\{\frac{1}{3}\}3}}{A_+^{\{0\}}B_+^{\{1\}}} = 3t \ll 1, \tag{14}$$

and this condition is fulfilled when $T_{\mathrm{c}1,2}$ are close. Such a two-gap system demonstrates analytically the smaller gap and the third derivative of free energy inflecting both at the very same temperature as interband coupling becomes vanishing. On the other hand, one obtains

$$\frac{T_{\mathrm{inf}}^{\Delta_2} - T_{\mathrm{inf}}^{\Delta f^{\mathrm{III}}}}{T_{\mathrm{inf}}^{\Delta_2}} = \frac{9}{2} t^{\frac{2}{3}} w^{\frac{2}{3}}, \tag{15}$$

i.e. an impact of the discrepancy between temperatures $T_{\mathrm{c}1,2}$ on the closeness of inflection points under interest may be compensated by the weakness of interband interaction. Our numerics presented in Fig. 2 verify that conclusion.

Last but not least, in the lowest order in w we have $\Delta_2(T_{\mathrm{c}2})^2 = y_+^{\{\frac{1}{3}\}}$, i.e.

$$\Delta_2(T_{\mathrm{c}2}) \sim W_{12}^{\frac{1}{3}}. \tag{16}$$

Therefore, the "susceptibility" related to the "field" W_{12} reads as

$$\frac{\partial \Delta_2(T_{\mathrm{c}2})}{\partial W_{12}} \sim W_{12}^{-\frac{2}{3}}. \tag{17}$$

Moreover, the lowest order term in $\Delta f'(T_{\mathrm{c}2})$ stemming from the weaker band is

$$\frac{2}{3}\frac{\rho_2}{T_{\mathrm{c}2}} y_+^{\{\frac{1}{3}\}} \sim W_{12}^{\frac{2}{3}}. \tag{18}$$

The corresponding term in $\Delta f''(T_{\mathrm{c}2})$ related to the same band equals

$$-\frac{2}{3}\frac{\rho_2}{T_{\mathrm{c}2}^2} A_+^{\{0\}} \sim W_{12}^{0}. \tag{19}$$

In the Landau mean-field theory of criticality the order parameter changes as $h^{\frac{1}{\delta}}$ ($\delta = 3$), susceptibility as $h^{\frac{1}{\delta}-1}$, entropy as h^{ϵ} ($\epsilon = \frac{2}{3}$) and heat capacity as $h^{-\alpha_{\mathrm{c}}}$ ($\alpha_{\mathrm{c}} = 0$) under applied external field h. Thus, interband coupling plays a role of external field governing the intrinsic criticality of weaker band. This consequence is in agreement with the critical exponent found for the corresponding healing length[29]. Note that intrinsic superconducting instability of the stronger band is affected in a qualitatively different way, for instance, $\Delta_1(T_{\mathrm{c}1}) \sim \sqrt{1 - \frac{T_{\mathrm{c}1}}{T_{\mathrm{c}}}} \sim W_{12}$ for vanishing interband interaction. That pairing rather shifts intrinsic phase transition from $T_{\mathrm{c}1}$ to T_{c}, but not smears it as in the case of weaker band.

IV. CONCLUSIONS

We have studied the interrelations between the thermodynamic features of two-gap superconductors (e.g. FeSe_{1-x}, $\mathrm{V_3Si}$) caused by former intrinsic phase transition in the weaker band. In particular, there appear atypical maxima in the temperature dependencies of entropy and heat capacity, and the gap kink in the weaker band. These peculiarities have slightly different locations on the temperature scale, and can move away from each other with decrease of interband coupling. The latter interaction is shown to play a role of external field which smears intrinsic superconducting instability of the weaker band.

ACKNOWLEDGMENTS

This study was supported by the European Union through the European Regional Development Fund (Centre of Excellence "Mesosystems: Theory and Applications", TK114) and by the Estonian Science Foundation (Grant No 8991).

Appendix: Solution in the vicinity of $T_{\mathrm{c}+}$

By introducing the notations $x = \Delta_2^2$, $\Delta = -\frac{a_2}{b_2}$ and $y^3 = -\frac{a_1\gamma^2}{b_1 b_2^2}$ one gets from system (10) the following equation

$$x\Big((x-\Delta)^3 - y^3\Big) = \frac{\gamma^2(\gamma^2 - a_1 a_2)}{b_1 b_2^3}. \tag{A.1}$$

As the condition $\gamma^2 - a_1 a_2 = 0$ determines the points $T_{\mathrm{c}\pm}$, we obtain $x_+ = \Delta_+ + y_+$ (index + implies $T = T_{\mathrm{c}+}$). Next we denote $\Delta_+ = \sum_{n=0}^{\infty} \Delta_+^{\{1+n\}}$ and $y_+ = \sum_{n=0}^{\infty} y_+^{\{\frac{1}{3}+n\}}$, and summation is made over the contributions of different powers of w (upper indexes in curly brackets). We also introduce the quantities $A = \frac{\rho_2}{b_2}$ and $B = \frac{\gamma^2}{b_2^2}$ for which $A_+ = \sum_{n=0}^{\infty} A_+^{\{n\}}$ and $B_+ = \sum_{n=0}^{\infty} B_+^{\{1+n\}}$. The first terms of these expansions are given in the main text, and

$$\Delta_+^{\{1\}} = A_+^{\{0\}} \frac{\rho_2}{\rho_1} t^{-1} w. \tag{A.2}$$

By differentiating Eq. (A.1) at $T_{\mathrm{c}+}$, we find the consecutive temperature derivatives of x. For instance, in the lowest order in w

$$x'_+ = \frac{1}{T_{\mathrm{c}+}} \frac{-2A_+^{\{0\}} y_+^{\{\frac{1}{3}\}2} + 6y_+^{\{\frac{1}{3}\}3} - A_+^{\{0\}} B_+^{\{1\}}}{3y_+^{\{\frac{1}{3}\}}\Big(y_+^{\{\frac{1}{3}\}} + \Delta_+^{\{1\}}\Big)}, \tag{A.3}$$

$$x''_+ = \frac{1}{T_{\mathrm{c}+}^2} \frac{\frac{2}{3}A_+^{\{0\}2} - 6A_+^{\{0\}} y_+^{\{\frac{1}{3}\}}}{3\Big(y_+^{\{\frac{1}{3}\}} + \Delta_+^{\{1\}}\Big)}, \tag{A.4}$$

etc. From these expressions one gets the value of Δ_2 and its derivatives at $T_{\mathrm{c}+}$. The analytic dependence $\Delta_2(T)$ is given then by Taylor series $\Delta_{2+} + \Delta'_{2+}(T - T_{\mathrm{c}+}) + \ldots$.

Usually w power of the lowest order contributions to the consecutive derivatives at $T_{\mathrm{c}+}$ decreases by $\frac{1}{3}$ as order of the derivative increases, for instance, $\frac{x''_+}{x^{\mathrm{III}}_+} \sim w^{\frac{1}{3}}$ or $\frac{\Delta^{\mathrm{III}}_{2+}}{\Delta^{\mathrm{IV}}_{2+}} \sim w^{\frac{1}{3}}$. However, sometimes corresponding w power decreases by $\frac{2}{3}$ due to extra vanishing of the terms. One notable example here is $\frac{\Delta''_{2+}}{\Delta^{\mathrm{III}}_{2+}} \sim w^{\frac{2}{3}}$, resulting in the solution of the equation $\Delta''_2(T_{\mathrm{inf}}^{\Delta_2}) = 0$ in the form

$$T_{\mathrm{inf}}^{\Delta_2} \approx T_{\mathrm{c}+} - \frac{\Delta''_{2+}}{\Delta^{\mathrm{III}}_{2+}} \approx T_{\mathrm{c}+}\left(1 + \frac{9y_+^{\{\frac{1}{3}\}2}}{2A_+^{\{0\}2}} + \frac{3B_+^{\{1\}}}{2A_+^{\{0\}} y_+^{\{\frac{1}{3}\}}}\right). \tag{A.5}$$

This value contains the lowest order correction to $T_{\mathrm{c}+}$ proportional to $w^{\frac{2}{3}} \sim W_{12}^{\frac{4}{3}}$. Note that zero (or negative) power of that correction disagrees with an assumption of the closeness to $T_{\mathrm{c}+}$ in case of small W_{12}.

By using free energy (8) rewritten in the form

$$\Delta f = b_2 x\Big(-x + \frac{\Delta}{2} + \frac{a_1 b_2}{2\gamma^2}(x-\Delta)^2\Big), \qquad \text{(A.6)}$$

we find that the situation with the consecutive temperature derivatives of Δf at $T_{\mathrm{c}+}$ is similar to that described above for the derivatives of the smaller gap. Here the suitable ratio of the derivatives occurs only for their higher orders, $\frac{\Delta f_+^{\mathrm{V}}}{\Delta f_+^{\mathrm{VI}}} \sim w^{\frac{2}{3}}$, resulting in the inflection point of $\Delta f^{\mathrm{III}}(T)$ in the form

$$T_{\mathrm{inf}}^{\Delta f^{\mathrm{III}}} \approx T_{\mathrm{c}+} - \frac{\Delta f_+^{\mathrm{V}}}{\Delta f_+^{\mathrm{VI}}} \approx T_{\mathrm{c}+}\left(1 + \frac{3B_+^{\{1\}}}{2A_+^{\{0\}} y_+^{\{\frac{1}{3}\}}}\right), \qquad \text{(A.7)}$$

i.e. the lowest order derivative of $\Delta f(T)$, which goes to zero sufficiently close to $T_{\mathrm{c}+}$, is $\Delta f^{\mathrm{V}}(T)$.

Finally, for weak interband coupling one has $\frac{T_{\mathrm{c}+}}{T_{\mathrm{c}2}} \approx 1 + o(w)$. Thus, the values $\Delta_2(T_{\mathrm{c}2}) = \sum_{n=0}^{\infty} \Delta_{2+}^{(n)} \frac{(T_{\mathrm{c}2}-T_{\mathrm{c}+})^n}{n!}$ or $\Delta f^{(m)}(T_{\mathrm{c}2}) = \sum_{n=0}^{\infty} \Delta f_+^{(n+m)} \frac{(T_{\mathrm{c}2}-T_{\mathrm{c}+})^n}{n!}$ (here n and m are the orders of the temperature derivative) contain the sum of w dependent contributions which become smaller and smaller as n increases. For tiny W_{12} these values are defined predominantly by $\Delta_2(T_{\mathrm{c}+})$ or $\Delta f^{(m)}(T_{\mathrm{c}+})$, correspondingly.

---

[*] teet.ord@ut.ee

[1] H. Suhl, B. T. Matthias, and L. P. Walker, Phys. Rev. Lett. **3**, 552 (1959); V. A. Moskalenko, Fiz. Met. Met. **8**, 503 (1959).

[2] L. Y. L. Shen, N. M. Senozan, and N. E. Phillips, Phys. Rev. Lett. **14**, 1025 (1965); R. Radebaugh and P. H. Keesom, Phys. Rev. **149**, 209 (1966); B. L. Blackford and R. H. March, *ibid.* **186**, 397 (1969); G. I. Lykken, A. L. Geiger, K. S. Dy, and E. N. Mitchell, Phys. Rev. B **4**, 1523 (1971).

[3] G. Binnig, A. Baratoff, H. E. Hoenig, and J. G. Bednorz, Phys. Rev. Lett. **45**, 1352 (1980).

[4] K. A. Müller, Nature **377**, 133 (1995); R. Khasanov, A. Shengelaya, A. Maisuradze, F. LaMattina, A. Bussmann-Holder, H. Keller, and K. A. Müller, Phys. Rev. Lett. **98**, 057007 (2007); R. Khasanov, S. Strässle, D. DiCastro, T. Masui, S. Miyasaka, S. Tajima, A. Bussmann-Holder, and H. Keller, *ibid.* **99**, 237601 (2007).

[5] S. Tsuda, T. Yokoya, T. Kiss, Y. Takano, K. Togano, H. Kito, H. Ihara, and S. Shin, Phys. Rev. Lett. **87**, 177006 (2001).

[6] A. A. Zhukov, L. F. Cohen, K. Yates, G. K. Perkins, Y. Bugoslavsky, M. Polichetti, A. Berenov, J. L. M. Driscoll, A. D. Caplin, L. Hao, and J. Gallop, Supercond. Sci. Technol. **14**, L13 (2001).

[7] Y. Wang, T. Plackowski, and A. Junod, Physica C **355**, 179 (2001); F. Bouquet, R. A. Fisher, N. E. Phillips, D. G. Hinks, and J. D. Jorgensen, Phys. Rev. Lett. **87**, 047001 (2001).

[8] K. Matano, Z. A. Ren, X. L. Dong, L. L. Sun, Z. X. Zhao, and G. Q. Zheng, Europhys. Lett. **83**, 57001 (2008); Y. L. Wang, L. Shan, L. Fang, P. Cheng, C. Ren, and H. H. Wen, Supercond. Sci. Technol. **22**, 015018 (2009); F. Hunte, J. Jaroszynski, A. Gurevich, D. C. Larbalestier, R. Jin, A. S. Sefat, M. A. McGuire, B. C. Sales, D. K. Christen, and D. Mandrus, Nature **453**, 903 (2008); P. Samuely, P. Szabó, Z. Pribulová, M. E. Tillman, S. Budko, and P. C. Canfield, Supercond. Sci. Technol. **22**, 014003 (2009); P. Szabó, Z. Pribulová, G. Pristáš, S. L. Budko, P. C. Canfield, and P. Samuely, Phus. Rev. B **79**, 012503 (2009).

[9] D. Daghero, M. Tortello, G. A. Ummarino, and R. S. Gonnelli, Rep. Prog. Phys. **74**, 124509 (2011); Y. Noat, T. Cren, P. Toulemonde, A. SanMiguel, F. Debontridder, V. Dubost, and D. Roditchev, Phus. Rev. B **81**, 104522 (2010); P. M. C. Rourke, M. A. Tanatar, C. S. Turel, J. Berdeklis, C. Petrovic, and J. T. Wei, Phus. Rev. Lett. **94**, 107005 (2005); K. Cho, H. Kim, M. A. Tanatar, J. Hu, B. Qian, Z. Q. Mao, and R. Prozorov, Phus. Rev. B **84**, 174502 (2011); Y. Singh, C. Martin, S. L. Budko, A. Ellern, R. Prozorov, and D. C. Johnston, *ibid.* **82**, 144532 (2010).

[10] A. Bussmann-Holder, A. R. Bishop, and A. Simon, Ferroelectrics **400**, 19 (2010).

[11] J. Rodrigo and S. Vieira, Physica C **404**, 306 (2004).

[12] Y. A. Nefyodov, A. M. Shuvaev, and M. R. Trunin, Europhys. Lett. **72**, 638 (2005).

[13] V. G. Kogan, C. Martin, and R. Prozorov, Phys. Rev. B **80**, 014507 (2009).

[14] R. Khasanov, M. Bendele, A. Amato, K. Conder, H. Keller, H.-H. Klauss, H. Luetkens, and E. Pomjakushina, Phys. Rev. Lett. **104**, 087004 (2010).

[15] S. Mukhopadhyay, G. Sheet, P. Raychaudhuri, and H. Takeya, Phys. Rev. B **72**, 014545 (2005); P. Raychaudhuri, G. Sheet, S. Mukhopadhyay, and H. Takeya, Physica C **460-462**, 95 (2007); Y. Naidyuk, D. Bashlakov, N. Bobrov, V. Chernobay, O. Kvitnitskaya, I. Yanson, G. Behr, S.-L. Drechsler, G. Fuchs, D. Souptel, D. Naugle, K. Rathnayaka, and J. R. Jr., *ibid.* **460-462**, 107 (2007).

[16] S. Kuroiwa, Y. Saura, J. Akimitsu, M. Hiraishi, M. Miyazaki, K. H. Satoh, S. Takeshita, and R. Kadono, Phys. Rev. Lett. **100**, 097002 (2008).

[17] M. Jourdan, A. Zakharov, M. Foerster, and H. Adrian, Phys. Rev. Lett. **93**, 097001 (2004).

[18] Y. Tokunaga, K. Ishida, Y. Kitaoka, K. Asayama, K. Tokiwa, A. Iyo, and H. Ihara, Phys. Rev. B **61**, 9707 (2000); A. Crisan, Y. Tanaka, A. Iyo, L. Cosereanu, K. Tokiwa, and T. Watanabe, *ibid.* **74**, 184517 (2006).

[19] H. Bluhm, N. C. Koshnick, M. E. Huber, and K. A. Moler, Phys. Rev. Lett. **97**, 237002 (2006).

[20] S. Kuzmicheva, T. Shanygina, S. Tchesnokova, and S. Krasnosvobodtsev, Solid State Commun. **152**, 119 (2012).

[21] R. S. Gonnelli, D. Daghero, M. Tortello, G. A. Ummarino,

V. A. Stepanov, J. S. Kim, and R. K. Kremer, Phys. Rev. B **79**, 184526 (2009).

[22] D. F. Agterberg, T. M. Rice, and M. Sigrist, Phys. Rev. Lett. **78**, 3374 (1997); M. E. Zhitomirsky and T. M. Rice, *ibid.* **87**, 057001 (2001); E. G. Maksimov, A. E. Karakozov, B. P. Gorshunov, E. S. Zhukova, Y. G. Ponomarev, and M. Dressel, Phys. Rev. B **84**, 174504 (2011); J. Annett, B. Györffy, G. Litak, and K. Wysokinski, Eur. Phys. J. B **36**, 301 (2003); E. J. Nicol and J. P. Carbotte, Phys. Rev. B **71**, 054501 (2005).

[23] A. Vargunin, T. Örd, and K. Rägo, J. Supercond. Nov. Magn. **24**, 1127 (2011).

[24] M. Silaev and E. Babaev, Phys. Rev. B **84**, 094515 (2011); G. Litak, T. Örd, K. Rägo, and A. Vargunin, Acta Phys. Pol. A **121**, 747 (2012); T. Örd, K. Rägo, and A. Vargunin, J. Supercond. Novel Magn. **25**, 1351 (2012).

[25] T. Örd, K. Rägo, and A. Vargunin, J. Supercond. Novel Magn. **22**, 85 (2009).

[26] P. J. Pereira, L. F. Chibotaru, and V. V. Moshchalkov, Phys. Rev. B **84**, 144504 (2011).

[27] R. Geurts, M. V. Miloševic, and F. M. Peeters, Phys. Rev. B **81**, 214514 (2010).

[28] E. Babaev, J. Carlström, and M. Speight, Phys. Rev. Lett. **105**, 067003 (2010).

[29] L. Komendová, Y. Chen, A. A. Shanenko, M. V. Miloševic, and F. M. Peeters, Phys. Rev. Lett. **108**, 207002 (2012).

[30] J. Hubbard, Phys. Rev. Lett. **3**, 77 (1959); R. L. Stratonovich, Sov. Phys. Dokl. **2**, 416 (1958).

[31] T. Soda and Y. Wada, Progr. Theor. Phys. **36**, 1111 (1966); T. Örd, K. Rägo, and A. Vargunin, "Physical properties of nanosystems, j. bonca and s. kruchinin (eds.)," (Springer, 2011) pp. 177–186.

[32] A. Wälte, S.-L. Drechsler, G. Fuchs, K.-H. Müller, K. Nenkov, D. Hinz, and L. Schultz, Phys. Rev. B **73**, 064501 (2006); T. M. McQueen, Q. Huang, V. Ksenofontov, C. Felser, Q. Xu, H. Zandbergen, Y. S. Hor, J. Allred, A. J. Williams, D. Qu, J. Checkelsky, N. P. Ong, and R. J. Cava, *ibid.* **79**, 014522 (2009); Y. Tanaka, A. Iyo, N. Shirakawa, M. Ariyama, M. Tokumoto, S.-I. Ikeda, and H. Ihara, J. Phys. Soc. Jpn. **70**, 329 (2001).

[33] F. Bouquet, Y. Wang, R. A. Fisher, D. G. Hinks, J. D. Jorgensen, A. Junod, and N. E. Phillips, Europhys. Lett. **56**, 856 (2001); Y. Nakajima, T. Nakagawa, T. Tamegai, and H. Harima, Phys. Rev. Lett. **100**, 157001 (2008); N. Oeschler, R. A. Fisher, N. E. Phillips, J. E. Gordon, M.-L. Foo, and R. J. Cava, Phys. Rev. B **78**, 054528 (2008); F. Hardy, T. Wolf, R. A. Fisher, R. Eder, P. Schweiss, P. Adelmann, H. v. Löhneysen, and C. Meingast, *ibid.* **81**, 060501 (2010); A. K. Pramanik, M. Abdel-Hafiez, S. Aswartham, A. U. B. Wolter, S. Wurmehl, V. Kataev, and B. Buchner, *ibid.* **84**, 064525 (2011); V. Guritanu, W. Goldacker, F. Bouquet, Y. Wang, R. Lortz, G. Goll, and A. Junod, *ibid.* **70**, 184526 (2004).

[34] T. Örd and N. Kristoffel, Physica C **370**, 17 (2002).

[35] Y. Tanaka, A. Iyo, N. Shirakawa, M. Ariyama, M. Tokumoto, S. I. Ikeda, and H. Ihara, Physica C **357-360**, 222 (2001).

[36] H. Kim, M. A. Tanatar, Y. J. Song, Y. S. Kwon, and R. Prozorov, Phys. Rev. B **83**, 100502 (2011).

[37] M. Silaev and E. Babaev, Phys. Rev. B **85**, 134514 (2012).

[38] A. V. Vagov, A. A. Shanenko, M. V. Miloševic, V. M. Axt, and F. M. Peeters, arXiv:1207.6297v1.